

## RADON EXHALATION FROM SELECTED BUILDING MATERIALS IN TANZANIA

**Aloyce Isaya Amasi<sup>1\*</sup>, Kelvin Mark Mtei<sup>2</sup>, Chau Nguyen Dinh<sup>3</sup> and Pawel Jodlowski<sup>3</sup>**

<sup>1</sup>Department of Research and Development, Tanzania Atomic Energy Commission, P. O. Box 743, Arusha Tanzania, <sup>2</sup>Department of Water and Environmental Science and Engineering, The Nelson Mandela African Institution of Science and Technology, P. O. Box 447, Tengeru, Arusha Tanzania

<sup>3</sup>Faculty of Physics and Applied Computer Science, AGH University of Science and Technology, Al.Mickiewicza 30, 30-059, Krakow, Poland

[\\*aaloyce@yahoo.com](mailto:aaloyce@yahoo.com), [amasia@nm-aist.ac.tz](mailto:amasia@nm-aist.ac.tz).

### Abstract

*The fraction of radon ( $^{222}\text{Rn}$ ) generated from building materials by the radioactive decay of radium  $^{226}\text{Ra}$  (progeny of  $^{238}\text{U}$ ) was measured by closed chamber method. The materials involved in this study include cements, gypsum, clay, sandstone and pozzolan which are commonly used directly as building materials. The indoor radon and annual effective doses contributions from the individual material have been derived from the mass exhalation coefficient. The mass exhalation coefficients generated vary from 0.7 to 2.8 % for cements and from 0.3 to 13 % for raw materials. Their indoor radon contribution ranged from 3.1-1012.3 Bq/m<sup>3</sup>; these values are in the permissible range of 600-1500 Bq/m<sup>3</sup> for dwellings and working places respectively as recommended by International Commission on Radiological Protection (ICRP) for building materials.*


**Keywords:** Building materials; Radon mass exhalation rate; Annual effective dose; Radiological hazard; Tanzania

### 1.0 INTRODUCTION

Radon  $^{222}\text{Rn}$ , thoron  $^{220}\text{Rn}$  and actinon  $^{219}\text{Rn}$  are naturally existing radioactive noble gases with half-lives of 3.83 d, 55.6 s and 3.96 s respectively. The source of the radioactive gases in the dwellings is the occurrence of the radium isotopes from the uranium and thorium series in the soil, rocks and building materials. From the radiological point of view,  $^{222}\text{Rn}$  is more hazardous since its half-life is significantly larger than those of  $^{220}\text{Rn}$  and  $^{219}\text{Rn}$ , therefore  $^{220}\text{Rn}$  and  $^{219}\text{Rn}$  are omitted in this study. At homes and building offices  $^{222}\text{Rn}$  emigrates from the walls, floor and ceilings and can accumulate to harmful levels. The primary concern of the health effects is related to the potential alpha energy concentration associated with the alpha particles emitted from the short-lived decay products of radon such as  $^{218}\text{Po}$  and  $^{214}\text{Po}$  (UNSCEAR 1988). The atoms of these isotopes at the moment they are generated often appear in the ion forms

chemically reactive and rapidly attach to the aerosols such as particles of dust and water vapor get inside the body through the process of inhalation. When inhaled may be deposited on respiratory tract tissues, decay and emit the alpha particles acting and damaging cells near the deposition site, contributing to increase the risk of lung cancer (Nazaroff 1992; Darby *et al.* 2005). The concentration of the radon daughters in the dwelling air are governed by radium concentration in the building materials including with floor, their construction, radon exhalation rate, attachment and recombination, deposition, and transport by diffusion and air ventilation condition and so on (Durrani 1997; Akerblom 1994; Jonsson 1995; Bossew 2003).

The release of the radioactive gas from the materials into the atmosphere is controlled by three processes: emanation, transport and exhalation. The illustration of the mentioned processes is presented in Figure 1.

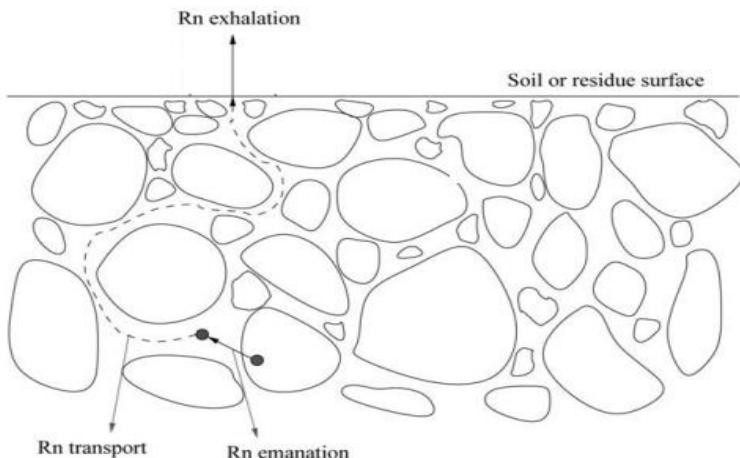

**Figure 1. Processes leading to the radon release to the atmosphere (IAEA, 2013)**

Emanation is the escape of the radon gas from the solid medium into the air filled pore spaces (interstitial space), governed by the momentum and recoil energy of alpha particles from the radioactive decay of radium. The recoil distance for  $^{222}\text{Rn}$  ranges 20-70 nm in common minerals, 100 nm in water, and 63 $\mu\text{m}$  in air (Nazaroff 1992). From the pores spaces (interstitial space), radon can migrate through diffusion process or seepage. The diffusion of radon is a process controlled by radon gas concentration gradient across the radon gas sources (rocks, soils, building materials, and other different materials) and the surrounding air. Finally, a fraction enters the atmosphere before undergoing radioactive decay the process known as exhalation. The exhalation rate is the radon fraction in the free

air originated from the radon created by the radium decays in the inside of the materials. It was revealed that, the value of exhalation rate depends on air condition and on the physical properties of the material samples such as moisture, grain sizes, and so on (De Martino 1998). The radon exhalation rate ranges from 0 (in the case of no radon release from the material), to 1 (where all radon escapes).

A number of studies have been conducted to establish the radium concentrations in raw and industrial building materials and their radon exhalation rate (EC 1999; Hassan *et al.* 2009; Sakoda *et al.* 2010; IAEA 2013). The  $^{226}\text{Ra}$  concentration of the most typical building materials in the World is summarized in Table 1 (IAEA 2002).

**Table 1 Concentration ranges  $^{226}\text{Ra}$  of the most typical building materials in the World (IAEA, 2002)**

Material	$^{226}\text{Ra}$ (Bq kg $^{-1}$ )	Material	$^{226}\text{Ra}$ (Bq kg $^{-1}$ )
Concrete	1-250	Cement	7 – 180
Clay (red) bricks	9 - 2200	Tiles (glazed and unglazed)	30 – 200
Sand-lime bricks/limestone	6 – 50	Phosphogypsum plasterboard	4 – 700
Natural building stones	1 – 500	Blast furnace slag stone and cement	30 – 120
Natural gypsum	< 1 - 70		

The Portland cements are typically the products derived from sedimentary or weathered rocks such as: sandstones, clay, limestone, shale, gypsum, pozzolan (UNSCEAR

2008). Portland cement clinker is manufactured by heating a calcareous material, typically limestone, and an argillaceous like clay or shale. The final

product of Portland cement is gained by intergrading gypsum (sulphate minerals) with the clinker (Taylor 1997). The production processes also influences the radionuclide activity concentration of final products and thus determine the activity concentrations in the construction materials. Generally, the radium concentration in the final product should be controlled by the radium activity of the raw materials and calculated by formula:

$$Ra_{prod.} = \sum_{i=1}^n w_i Ra_i \quad (1)$$

where  $Ra_{prod.}$  and  $Ra_i$  are the concentrations of radium in cement and  $i$ -th raw material composition respectively;  $w_i$  – weight contribution of the  $i$ -th composition.

The aim of this work is to determine the  $^{222}\text{Rn}$  mass exhalation rates of Tanzania cements and selected building materials by closed chamber method and to estimate their contributions to

indoor  $^{222}\text{Rn}$  concentration. The obtained results were used for assessment of the adequate radiological indices, and evaluating the investigated building materials from the radiological point of view.

## 2.0 MATERIALS AND METHODS.


A number of methods have been developed to measure the radon exhalation rates of building materials including the accumulation method, the charcoal method, the SSNTD (solid state nuclear track detector method (Limoto *et al.* 2008) and the closed chamber method (CCM). All methods have one feature in common that is measuring radon concentration in a closed space after the radioactive secular equilibrium between radon and radium is achieved. In this study the closed chamber method was adopted using the radon chamber coupled with radon meter "Pylon AB5™ (Figure 2).



Figure 2. The view of the measurement device

The four brands of cement available in Tanzania trademarked as Tembo, Simba, Rhino and Kilwa, collected from the local market were examined in this study. The other selected building material includes pozzolan; occasionally used for plastering (with few centimetres thin wall) in local communities, gypsum as thin (1-3 cm) gypsum boards for walls and ceilings and clay and sandstone for

fired and unfired bricks. Pozzolan, clay, sandstone and gypsum were collected from their respective quarries in Songwe and Kilwa located in Mbeya and Lindi regions respectively. The samples were collected according to IAEA, (1989) standard sampling procedures for environmental sampling; the localizations of the collected samples are shown on Figure 3.

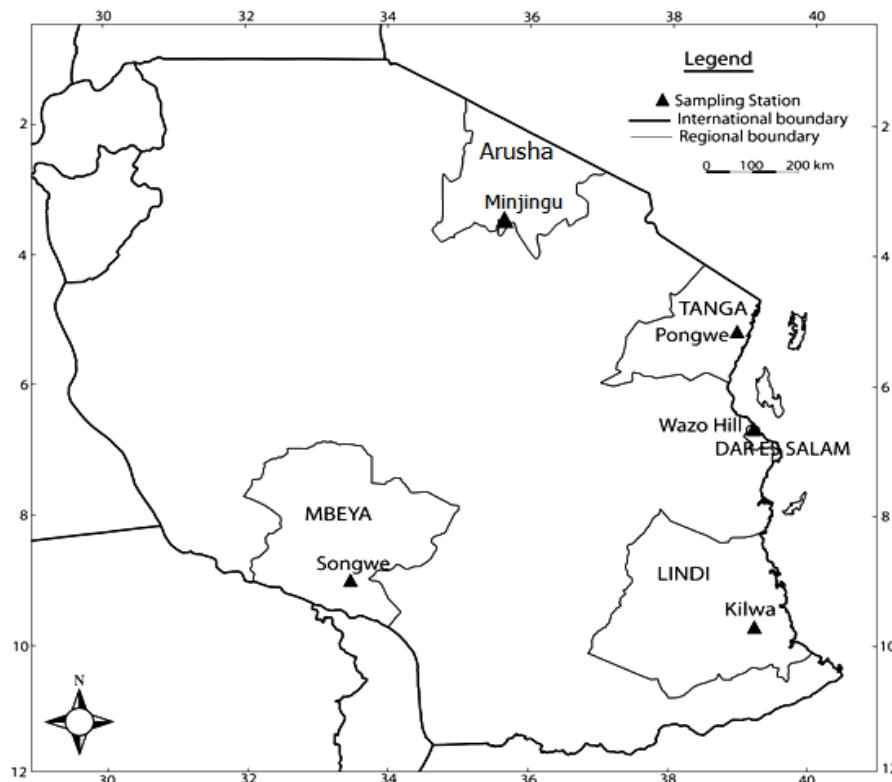

**Figure 3. Sketch of Tanzania showing sampling sites (names of the regions in capital letters)**

The sample under investigation weighed from 0.5 to 1 kg were milled until the grain sizes lower than 1 mm and dried at 105°C for 24 hours and placed inside the exhalation chamber of volume of 10 dm<sup>3</sup> and tightly sealed to prevent escape of radon. Each enclosed sample was left for one month to establish the equilibrium between the <sup>226</sup>Ra and <sup>222</sup>Rn. After attainment of the equilibrium the closed chamber was connected with AB-5 Pylon coupled with the Lucas cell by using the plastic pipes and valves (see Figure 2). The inlet and outlet located on the top of the chamber with the inlet tube extended down to the bottom of the chamber.

The AB-5 is built in pump that circulates the air through circuit connecting the chamber and Lucas cell. For establish the uniform distribution of the air in the circuit and to gain the minimum uncertainty, the AB-5 was allowed to pump the air for 30 minutes and counts were collected for several runs, every counting run was lasting for 2 hours. The total activity of radon released from the sample material into the air is evaluated by measured radon content in the Lucas cell and the effective volume of the measurement system. The effective volume is determined by

considering the volumes of the chamber, closed vessel, all pipes inside the closed vessel, the loop system for radon measurement and of the Lucas cell (IAEA 2013). The total Rn produced in the closed chamber was obtained by multiplying the sample mass and adequate radium activity of the investigated material. The mass exhalation rate therefore is given by the following expression (IAEA2013).

$$E_m = \frac{C_d}{mRa} \quad (2)$$

where  $E_m$  is the mass exhalation rate;  $m$  is the mass of the sample (kg); and  $Ra$  is the radium activity concentration (Bq kg<sup>-1</sup>) of the investigated material.

$C_d$  is the radon content in the sampling device (Bq) and calculated using formula  $C_d = (C_L \cdot V_d) / V_L$

Where  $V_d$ ,  $V_L$  are the effective volume of the sampling device and Lucas cell respectively;  $C_L$  – radon content in Lucas cell, and calculated by formula:  $C_L = NCR / (3 \cdot \varepsilon \cdot t)$ , where  $\varepsilon$  - recorded alpha efficiency of AB-5 device and  $t$  - measurement time in seconds;

*NCR* – net count rate obtained by subtracting the measured count rate after pumping from the background one (the count rate measured for the same Lucas cell before pumping air). The background measurements were performed before pumping for the used Lucas cell. The background measurement time was predicted for the relative uncertainty of count rate lower than 2 %.

The mass exhalation rate was then used to determine the potential radon concentration originating from the building materials in the air inside the “standard room” of  $4 \times 5 \times 2.8$  m ( $56 \text{ m}^3$ ) with door of  $1 \text{ m} \times 1.8 \text{ m}$  and window of  $1.4 \text{ m} \times 1.4 \text{ m}$  dimensions according to the EC Standards (EC1999). The wall thickness is often upon on the application of the building materials. For instance the thickness of the wall built of gypsum is assumed to be 3 cm, of pozzolan and soil 1 cm each, cements bricks 20 cm and that from clay and sandstone bricks the thickness amounts to 10 cm each (EC1999). The radon contribution from the building material was estimated as follows

$$C_{Rn} = \frac{A_{Ra} \cdot E_m \cdot M}{V} \quad (3)$$

where  $C_{Rn}$  is concentration of the radon originating from the building material,  $A_{Ra}$  and  $E_m$  are the activity concentration of radium and mass exhalation rate of the building material respectively.  $V$  is the volume of the room and  $M$  is the mass of the walls and estimated by formula  $(2 \times 2.8 \times (4+5) - (1 \times 1.8 + 1.4 \times 1.4)) \text{ m}^2 \times a \text{ (m)} \times \rho(\text{kg m}^{-3})$  for standard room; where  $a$  is the wall thickness and  $\rho$  is the building material density. The density of every investigated material was determined by weight and the sample volume of the milled material and summarized in Table (3).

The radiological hazard is directly connected with the potential energy alpha concentration originated from the alpha particles emitted from the decay of radon progeny and expressed in  $\text{J/m}^3$  or Working Level (WL) unit (WHO 2009). The worker's/dwellers exposure to radon daughters is expressed in units of Working Level Months (WLM). Working level month is equivalent to the exposure at an average concentration of 1 WL for 170 working hours (WHO 2009; ICRP 1993).

The annual potential alpha energy potential expressed in WLM for dwelling habitant is estimated by formula (Sharma *et al.* 2012):

$$E(WLM / y) = \frac{8760 \times n \times F \times C_{Rn}}{170 \times 3700} \quad (4)$$

where  $n$  is the fraction of time spent indoors and arbitral assumed to be equal to 0.8;  $F$  is the equilibrium factor between  $Rn$  and its progeny and assumed to be equal to 0.42;  $C_{Rn}$  – radon concentration in the air [ $\text{Bq m}^{-3}$ ], 8760 is the number of hours per year; and 170 is the number of hours per working month (UNSCEAR 2000). The annual potential alpha energy can be translated to the annual effective dose by multiplication of the alpha energy potential and a conversion factor of 3.88mSv/WLM. By this way the annual effective dose is expressed in mSv(ICRP 1993). The uncertainty of radon mass exhalation rate can be calculated using the equation (2) and propagation low as follows.

$$\frac{uE_m}{E_m} = \left[ \left( \frac{uC_d}{C_d} \right)^2 + \left( \frac{uM}{M} \right)^2 + \left( \frac{uR_a}{R_a} \right)^2 \right]^{1/2} \quad (5)$$

Where  $uE_m$ ,  $uC_d$  and  $uRa$  are the uncertainties of measured radon content in the chamber, sample mass and  $^{226}\text{Ra}$  concentration of the investigated material.

### 3.0 RESULTS AND DISCUSSION

The measured radon mass exhalation rates, their uncertainties,  $Rn$  concentrations and annual effective doses estimated for the standard room built from the investigated materials are summarized in Table 2. The radon mass exhalation ranges from 0.3 to 13 % for raw materials and from 0.7 to 2.8 % for cements. The variation in the mass exhalation rate of cements is due to radioactivity characteristics of the individual cements and mineral structure of their components.

**Table 2: The estimated Rn concentration and annual effective doses (E) resulted from the released radon from the wall built from investigated materials**

Material	$^{226}\text{Ra}$ (Bq kg <sup>-1</sup> ) <sup>1</sup>	Density (kg m <sup>-3</sup> )	Net count rate 2h	$E_m$ (%) per	Rn (Bq m <sup>-3</sup> )	Annual effective dose mSv
Rhino cement	60.7±2.7	1112	124±33	1.2±0.3	134.9	2.3
Tembo cement	55.8±4.3	1187	327±52	2.8±0.4	308.9	5.3
Kilwa cement	29.7±4.0	1106	51±30	0.7±0.4	38.3	0.7
Simba cement	38.3±3.9	1123	107±27	1.0±0.3	71.6	1.2
Pozzolan	93.6±1.3	1385	4500±903	12.0±2.4	129.6	2.2
Soil	120.3±1.6	1023	120±26	0.3±0.1	3.1	0.05
Gypsum	7.6±0.4	1105	119±22	13.0±2.4	27.3	0.5
Sandstone	25.3±0.7	1347	193±27	2.0±0.1	56.7	0.9
Clay	91.0±1.3	1113	3750±612	12.0±0.02	1012.3	17.5

<sup>1</sup> the  $^{226}\text{Ra}$  concentrations of the investigated materials were measured by gamma spectrometry (Amasi *et al.* 2014)

The indoor radon concentrations and annual effective doses estimated for hermetically closed "standard room" with the assumption that the exhaled radon was only released from its walls built from the investigated materials. The calculated indoor radon concentration and annual effective dose ranged from 3.1 to 1012.3 Bq m<sup>-3</sup> and from 0.05 to 17.5 mSv respectively. These values were within the safe limits of radon potential health hazards of 600

Bq m<sup>-3</sup> for dwellings and 1500 Bq m<sup>-3</sup> for workplaces corresponding to annual dose limits of 10 and 20 mSv respectively (ICRP 1993, 2009).

It is customarily understood that the radon content in the air is the quantity of radium in the building materials (Figure 4).

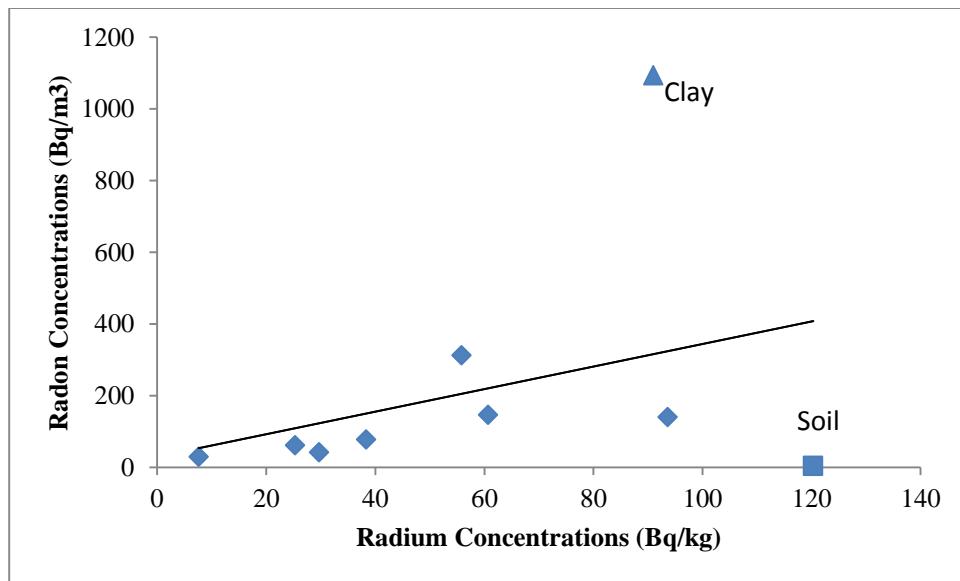


Figure 4. A graph of Rn concentration in the air versus Ra concentrations in the sample material

However, some discrepancies were observed due to other parameters such as mineral structure, chemical composition and so on. For instance, the slight elevation of the mass emanation rate and annual effective dose exposure from Tembo cement should be connected with radium quantity and its distribution in the volcanic pozzolan and clay. Due to characteristics of the adsorption processes the distribution of the radium atoms in the pozzolan and clay may be closer to the particle surfaces and this orientation enhances the radon escape from the grain space to the air. It was observed that radon exhalation rate from the soil was significantly lower than the rest of the materials; this fact can be connected with the occurrence of organic fractions in the soil, which often contains a lot of the water particles in their cell structures. Water can act as the shield for Rn atoms escape from the solid material to the air (Bossew 2003).

#### 4.0 CONCLUSIONS

Radon mass exhalation rates of Tanzania cements, gypsum and pozolan have been determined by closed chamber method. On the basis of the obtained results, the indoor radon contribution of each individual material has been estimated. All of the calculated indoor radon exposure values are less than the international recommended indoor <sup>222</sup>Rn exposure limits. The annual effective doses were also determined and found to be within the permissible range. The difference in radon mass exhalation rates supports the suggestion that radon emanation is a function of Ra concentration, moisture and particle structure of building materials. Based on the measured mass emanation rate, calculated Rn concentration and related effective dose, one can state that the investigated materials are safe for the dwellers whenever used for construction purpose.

## 5.0 RECOMMENDATIONS

Radon in homes and workplaces needs exceptional attention because its contribution to radiation dose is as higher 50% greater than those from almost any other source both natural and manmade radiation sources (UNSCEAR, 2000). It is therefore vital and imperative to understand its generation, release mechanisms from different materials, migration from this material and finally the entering process into outdoor atmosphere and indoor to our houses and our working places. This study has given rise to a number of potential future research projects about natural radioactivities and radon and a number of recommendations have been drawn.

i. Radon emanation and exhalation is a function of the meteorological parameters. Study of the radon exhalation processes in connection with the meteorological conditions is highly recommended for better understanding the processes.

ii. Applications of radon remediation methods in dwellings with increased radon concentrations are advisable followed by the appropriate actions to minimize exposure from the building designing and construction stage. The knowledge of preventing radon entrance in building from the soil through gap sealing and ventilation of the house is required. Other means include pore filling, surface coating by painting and the like.

iii. Conduct studies aiming at mapping regions, sites and building characteristics likely to be associated with high radon levels.

iv. Similar studies can be carried out in uranium mines and other convection mining sites for determination of radon concentration. It is noteworthy to discern the radium activity concentration in the soil and building materials because radon exhalation rate depends on it.

v. Future studies to generalize radon fractions trends for many different materials with different mineral contents and from different geological origins would be beneficial. On the basis of the results obtained, one would be able to predict, the kind of minerals responsible for radon exposure to human without detailed emanation tests. A further study however is suggested to be done to

investigate the quantities of the chemical elements in the elevated samples for instance pozzolan from Songwe using Atomic Absorption Spectroscopy. The results will be useful to provide a clear explanation of the radioactivity contribution of chemical species present in the cements.

vi. Future studies should also be conducted to establish the data base of the natural radioactivity in local and imported building materials for future construction monitoring in Tanzania. The data base will be used to aid the relevant authorities in establishing the regulations, standards or codes for construction practices under which the recommended level might otherwise be exceeded. The purpose of setting controls on the radioactivity of building materials is to limit the radiation exposure due to materials with enhanced or elevated levels of natural radionuclides.

## REFERENCES

Akerblom, G. (1994), "Radon in water", *Environmental Health* 3, NEHA, 30-35.

Bossew, P (2003), "Radon emanation power of building materials, soils and rocks", *Applied Radiation Isotopes* 59, Elsevier, 389-392.

Darby, S., Hill, D., Auvinen, A., Barros-Dios, J.M., Baysson, H., Bochicchio, F., Deo, H., Falk, R., Forastiere, F., Hakama, M., Heid, I., Kreienbrock, L., Kreuzer, M., Lagarde, F., Mäkeläinen, I., Muirhead, C., Oberaigner, W., Pershagen, G., Ruano-Ravina, A., Ruosteenaja, E., Schaffrath, R.A., Tirmarche, M., Tomášek, L., Whitley, E., Wichmann, H.E. & Doll, R. (2005), Radon in homes and risk of lung cancer: collaborative analysis of individual data from 13 European case-control studies. *British Medical Journal* 330(7485), 223-227.

De Martino, S., Sabbarese, C., Monetti, G. (1998), "Radon Emanation and Exhalation Rates from Soils Measured with an Electrostatic Collector", *Applied Radiation Isotopes* 49, Elsevier, 407-423.

Durrani, S.A., Ilic, R. (1997), (Eds.) "Radon measurements by etched track detectors", Applications in Radiation Protection, Earth Sciences and the Environments, World Scientific, Singapore.

EC, (1999), European Commission. Radiological Protection Principles Concerning the Natural Radioactivity of Building Materials Radiation Protection 112, European Commission, Luxembourg, ISBN: 92-828-8376-0.

IAEA, (1989), "Measurement of Radionuclides in Food and the Environment", A Guidebook Technical reports series, No STI/DOC/10/295, International Atomic Energy Agency, Vienna.

IAEA, (2002), "The extent of environmental contamination by naturally occurring radioactive material (NORM) and technological options for mitigation", IAEA draft Technical Report, Vienna.

IAEA, (2013), "Measurement and Calculation of radon releases from NORM residues", Technical Reports Series no. 474.

ICRP, (1993), International Commission on Radiological Protection. "Protection Against Radon-222 at Home and at Work," ICRP Publication 65. Annals of the ICRP 23.

ICRP, (2009), International Commission on Radiological Protection Statement on Radon. "Protection against Radon-222 at Home and at Work," ICRP Publication 65 Annals of the ICRP 23 (2).

Hassan, M.N., Masahiro, H., Tetsuo, I., Atsuyuki, S., Sarata, K., Sahoo, S.T., Masahiro, F. (2009), "Radon Migration Process and Its Influence Factors" Review, *Japanese Journal of Health Physics* 44(2), 218-231.

Limoto, T., Akasaka, Y., Koike, Y. & Kasoko, T. (2008), "Development of a technique for the measurement of the radon exhalation using an activated charcoal collector", *Journal of Environmental Radioactivity* 99, Elsevier, 587-95.

Jonsson, G. (1995), "Radon gas – where from and what to do?", *Radiation Measurements* 28, Elsevier, 537-546.

Nazaroff, W.W. (1992), "Radon transport from soil to air", *Reviews of Geophysics* 30, AGU Publications, 137-160.

Sakoda, A., Nishiyama, Y., Hanamoto, K., Ishimori, Y., Yamamoto, Y., Kataoka, T., Kawabe, A., Yamaoka, K. (2010), "Differences of natural radioactivity and radon emanation fraction among constituent minerals of rock or soil", *Applied Radiation Isotopes* 68, Elsevier, 1180-1184.

Sharma, J., Mahur, A. K., Kumar, R., Vashney, R., Sonkawde, R. G., Swarup, R., Singh, H., Prasad, R. (2012), "Comparative study of indoor radon, thoron with radon exhalation rate in soil samples in some historical places at Jaipur, Rajasthan, India". *Advanced Applied Science Research*, 3(2), 1085-1091.

Taylor, H. F. W. (1997), *Cement Chemistry*: Thomas Telford Publishing, London.

UNSCEAR, (1988), Sources and effects of ionizing radiation, Report to the General Assembly, with Annexes, United Nations, New York.

UNSCEAR, (2000), Sources and effects of ionizing radiation, Report to the General Assembly, with Annexes, United Nations, New York.

UNSCEAR, (2008), Sources and effects of ionizing radiation, Report to the General Assembly, with Annexes, United Nations, New York.

World Health Organization, (2009), "WHO handbook on indoor radon: a public health perspective", Geneva, Switzerland.

Zhang, L., Lei, X., Guo, Q., Wang, S., Ma, X., Shi, Z. (2012), "Accurate measurement of the radon exhalation rate of building materials using the closed chamber method". *Journal of Radiological Protection* 32, IOP Science, 315-323.